

~~537~~
537

Using Self-Assembled Monolayers to Study the Interactions of
Man-Made Materials with Proteins

Margaret V. Merritt,[†] Milan Mrksich and George M. Whitesides*

Harvard University
Department of Chemistry
12 Oxford Street
Cambridge, Massachusetts 02138

[†] on sabbatical leave from Wellesley College, Department of Chemistry, Wellesley,
Massachusetts 02181.

Overview

The first event that occurs on contact of a synthetic material with a medium containing dissolved protein--such as blood or plasma--is the adsorption of protein to the surface. Other responses, including the attachment of cells and organization of tissue, are secondary and depend on the nature of the adsorbed layer of protein. Despite the identification of many surfaces suitable for biomedical applications, the molecular details of the processes by which proteins adsorb to solid surfaces are not completely understood. This understanding has been limited in large part by a lack of well-defined surfaces whose properties could be tailored at the molecular scale. Self-assembled monolayers (SAMs) constitute a class of model surfaces particularly well suited for studying interactions of proteins and cells with surfaces. The ability to control the composition and properties of SAMs--particularly SAMs formed upon the absorption of long-chain alkanethiols on gold--through synthesis combined with simple methods for patterning their functional groups in the plane of the monolayer, make this class of surfaces the best currently available for fundamental molecular mechanistic studies of protein adsorption and cell adhesion. This chapter reviews the use of two classes of SAMs--alkanethiolates on gold and alkylsiloxanes on surfaces presenting hydroxyl groups--for studies of protein adsorption and cell attachment.

Background

Protein Adsorption. The interactions of proteins with man-made surfaces have been studied extensively;¹⁻⁶ early studies were motivated by the development of blood compatible materials and devices.⁷ The process of adsorption is complicated and depends on the characteristics of the protein, the interface and the solution. Even in the case of a single protein adsorbing to a structurally-defined and homogeneous surface, the protein may adsorb in multiple orientations and conformations and in differing microenvironments created by neighboring proteins (Fig. 1). A recent report describing

Figure 1. Scheme illustrating the complexities associated with studies of protein adsorption. A protein that adsorbs to the surface may also desorb with no change in its structure and function (a). The adsorbed protein may diffuse on the surface (b) and then desorb (c), or undergo a conformational change (d) and desorb (e) or remain irreversibly adsorbed (f). In some cases, the adsorbed protein may be displaced from the surface by another protein in solution (g; the "Vroman effect," 7, 20). This scheme is not complete, but is further complicated by the many different orientations, conformations, and environments available to an adsorbed protein.

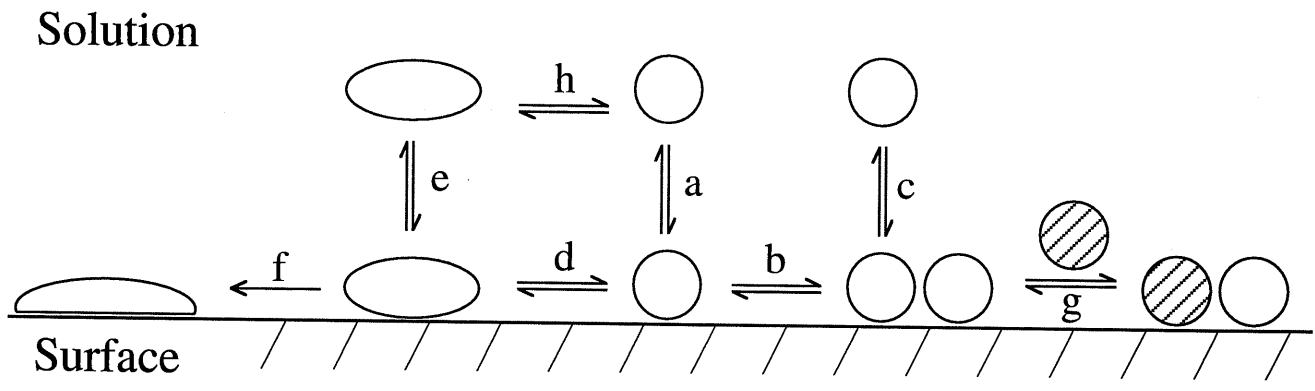


Fig. 1


the changes in adsorption kinetics of the soluble core tryptic fragment of cytochrome *b5* due to a single amino acid substitution emphasizes the need to understand protein adsorption at the molecular level.⁸

Methods to Characterize Protein Adsorption. The amounts and rates of protein adsorption have been determined by techniques that measure the dielectric properties at an interface [surface plasmon resonance (SPR) spectroscopy,^{9,10} waveguide interferometry,¹¹ and ellipsometry¹²] or changes in the resonance frequency of piezoelectric materials.¹³ Although these techniques give no direct information regarding the orientation and structure of adsorbed protein, they provide information that is qualitatively related to conformational changes of adsorbed proteins. Lee and Belfort interpreted the increase in the enzymatic activity of RNase A adsorbed on mica with increasing residence times in terms of a reorientation of the adsorbed protein that made the active site more accessible to the solution.¹⁴ Conformational changes in BSA adsorbed to fluoropolymer surfaces were correlated to cell adhesion using fluorescent tagging methods.¹⁵ Spectral techniques that are common in characterizing soluble proteins--such as circular dichroism^{16,17} and infrared spectroscopies¹⁸--are limited by their sensitivity for studying adsorbed proteins.


Molecular-Scale Characterization. Robertson and coworkers used a panel of monoclonal antibodies having defined epitopes against myoglobin to probe the orientation of the protein adsorbed to mica surfaces.¹⁹ Vroman and colleagues used similar antisera methods in pioneering studies of adsorption of serum proteins to biomaterials.^{7, 20} This strategy, and related "footprinting" strategies²¹--using either chemical reagents or proteases--provide direct, but low resolution, information about protein topology at surfaces. For special cases where the protein layer is ordered, other techniques can provide direct structural information: Caffrey and coworkers, for example, used X-ray

Figure 2. Representations of self-assembled monolayers (SAMs) of alkanethiolates on gold (A) and alkylsiloxanes on hydroxylated surfaces (B). The alkyl chains of the alkanethiolates pack in a quasi-crystalline array; the alkyl chains of the alkylsiloxanes are less ordered. The properties of both classes of SAMs are determined primarily by the terminal functional group X.

A

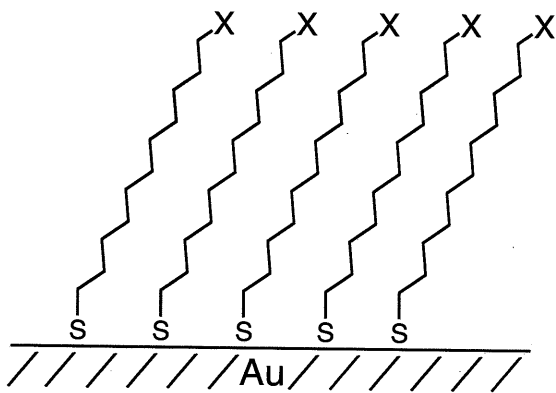


B

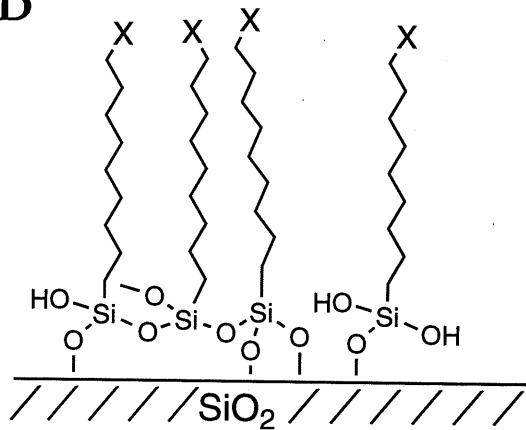

standing wave methods to characterize the orientation of cytochrome c adsorbed to a silver surface;²² Kornberg and coworkers used electron diffraction to determine the structure of a two-dimensional crystal of streptavidin adsorbed to a biotinylated lipid layer.²³

Self-Assembled Monolayers

Alkanethiolates on Gold. Self-assembled monolayers of alkanethiolates on gold form upon the adsorption of long chain alkanethiols, RSH [R = X(CH₂)_n, n = 11-18] from solution (or vapor) to a gold surface:



The structure of these SAMs is well established (Fig. 2).^{24,25} The sulfur atoms coordinate to the three-fold sites of the gold(111) surface. The close-packed alkyl chains are trans-extended and tilted approximately 30° from the normal to the surface. The terminal functional group X is presented at the surface and determines the properties of the interface. Even complex groups can be incorporated through modest synthetic effort; alternatively, groups can be introduced onto the surface after the SAM is formed. The properties of SAMs can be controlled further by formation of "mixed" SAMs from solutions of two or more alkanethiols. SAMs on gold are stable in air or in contact with water or ethanol for periods of several months; the thiolates desorb at temperatures greater than 70°C and are photo-oxidized when irradiated with UV light in the presence of oxygen. SAMs have sufficient stability in aqueous media for use in cell culture for periods of days. The optical transparency of the system of SAMs on gold depends on the thickness of the underlying gold; gold films 100 Å in thickness are optically transparent; gold films 2000 Å in thickness are opaque and reflective. Even the thinner films of gold are electrically conductive.

Alkylsiloxanes. Alkylsiloxane monolayers are formed by reaction of a hydroxylated surface (usually glass or silicon oxide) with a solution of alkyltrichlorosilane (or alkyltriethoxysilane).²⁶⁻²⁷ The structure of these monolayers is not as well established as those of alkanethiolates on gold, and depends on the conditions used to prepare the SAMs.^{26, 28} The siloxane groups cross-link with each other and with hydroxyl groups of the surface, though the relative importance of the two interactions is still not completely understood.²⁹ Alkyl siloxane SAMs are significantly more stable thermally than alkanethiolates on gold and do not require the deposition of a layer of metal for the preparation of substrates. They have the disadvantages that they are structurally less ordered than alkanethiolates on gold and are limited in the range of functional groups that can be incorporated directly--without carrying out reactions at the surface--by the reactivity of the alkyltrichlorosilane precursors.

Interactions of Proteins with SAMs

Non-specific adsorption. Hydrophobic forces appear to dominate the interactions of proteins with surfaces in many systems. Many studies have found that the adsorption often increases with the hydrophobicity of both the surface and the protein.^{30,31} The amount of several proteins adsorbing to SAMs on gold presenting a wide range of functional groups correlated with the hydrophobicity of the SAM.³² The protein layer is usually irreversibly bound to hydrophobic surfaces, but can be removed with detergents, or by exchange with other proteins in solution--the "Vroman effect."²⁰ The role of electrostatic interactions in adsorption has been less well studied. In a recent study using SAMs with charged functional groups, Tengvall and coworkers showed that the adsorption of each of five serum proteins showed a different dependence on type of surface charge.³³

Protein-Resistant Materials. An important goal in biomaterials is the development of "inert" materials that resist protein adsorption. A common method to passivate surfaces towards protein adsorption is to modify the surface with poly(ethylene glycol) (PEG); several strategies have been devised to immobilize this polymer at surfaces.³⁴⁻³⁶ Another common strategy is to coat the surface with a protein, usually bovine serum albumin, that resists the adsorption of other proteins. This latter method has the advantages that it is simple and inexpensive, but suffers from limited stability of the protein layer owing to exchange with other proteins in solution, and presentation of biologically active peptide sequences.

SAMs Presenting Ethylene Glycol Groups. We found that SAMs on gold prepared from alkanethiols terminated in short oligomers of the ethylene glycol group $[\text{HS}(\text{CH}_2)_{11}(\text{OCH}_2\text{CH}_2)_n, n = 2-7]$ resisted entirely the adsorption of several proteins.^{37,38} Even SAMs containing as much as 50% hydrophobic methyl-terminated alkanethiolates, if mixed with oligo(ethylene glycol)-terminated alkanethiolates, resisted the *in situ* adsorption of protein. The basis for protein resistance in this system is not well understood. DeGennes and Andrade have proposed that surfaces modified with *long* PEG chains resist the adsorption of protein by "steric stabilization;" where adsorption of protein to the surface causes the solvated and disordered glycol chains to compress; the energetic penalty of desolvating the glycol chains and restricting the conformational freedom of the chains both serve to resist adsorption. It is unclear whether this mechanism applies to *short*, densely-packed oligo(ethylene glycol) chains.³⁹

Covalent Immobilization of Proteins to SAMs. Methods that use covalent immobilization to confine proteins at interfaces have many advantages over those that rely on physical adsorption of protein layers, especially when well-defined surfaces are employed. Covalently attached layers of protein cannot dissociate from the surface, or exchange



with other proteins in solution. A variety of selective chemistries can be employed to provide high levels of control over the adsorption process. For example, Bohn, Sligar, and coworkers used genetic engineering to construct a mutant of cytochrome c that had only a single cysteine group; immobilization of this protein to a SAM terminated in thiol groups gave a uniformly oriented layer of protein.⁴⁰

Bio-Specific Adsorption of Protein. The synthetic flexibility offered by SAMs of alkanethiolates make these surfaces useful for studies of bio-specific adsorption. Several groups have characterized the recognition of antigens immobilized on SAMs by antibodies.⁴¹ Spinke et al used SPR to study the specific binding of streptavidin to SAMs terminated in biotin groups.⁴² We have used the combination of SPR and SAMs presenting oligo(ethylene glycol) groups as supports to which ligands were attached for studies of reversible bio-specific recognition by proteins. SAMs presenting a Ni(II) complex selectively bound proteins whose primary sequence terminated with a histidine tag, a modification often incorporated into recombinant proteins to facilitate purification.⁴³ In a similar system, SPR was used to characterize the binding of carbonic anhydrase to SAMs presenting benzenesulfonamide groups (Fig. 3).⁴⁴ In both cases, the amount of adsorbed protein increased with density of the ligand on the surface and the surfaces resisted non-specific adsorption of other proteins. These SAM systems are especially well-suited for fundamental studies of bio-molecular recognition at surfaces because both the density and environment of immobilized ligands can be controlled.

Attachment of Cells to SAMs

The attachment and spreading of anchorage-dependent cells is mediated by proteins of the extracellular matrix (ECM); e.g., fibronectin, laminin, collagen and others. Bio-specific recognition of peptide sequences of the ECM by membrane proteins of the cells is important in these processes; the best understood of these interactions is the binding of

Figure 3. Surface plasma resonance spectroscopy measures the rate and quantity of binding of carbonic anhydrase (CA) to a mixed SAM presenting oligo(ethylene glycol) and benzenesulfonamide groups (A). The change in resonance angle ($\Delta\theta$) of reflected light from gold interface is shown as a function of time (B). The mixed SAM resists the non-specific adsorption of protein from a solution containing β -casein, myoglobin, alcohol dehydrogenase, trypsin inhibitor, acylase I, α -lactalbumin, cytochrome c, fibrinogen, and RNase A (0.2 mg/ml each; these proteins were chosen arbitrarily from those readily available, and were intended only to test specificity) (bottom curve). When CA (5 mM) was present in this sample, however, SPR measured adsorption of the protein (upper curve).

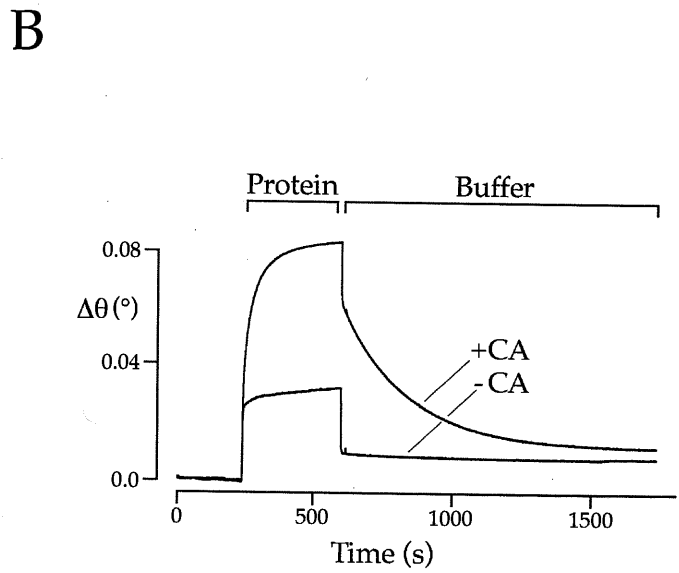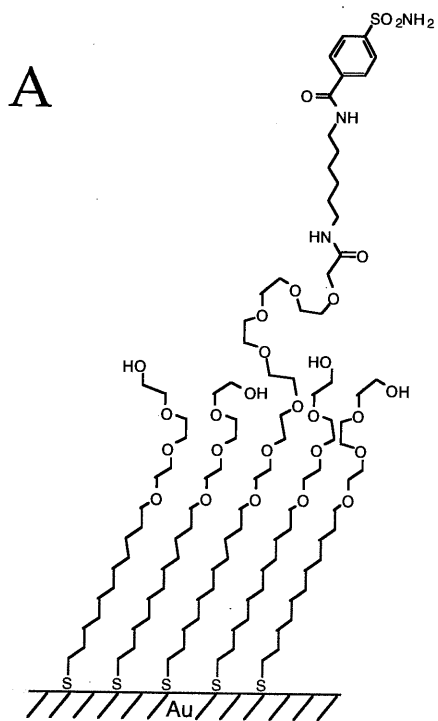

the peptide sequences RGD and YIGSR by cellular integrins. Consequently, the identity of the protein layer, and the molecular conformations of the proteins within the layer are important for cell attachment. Both hydrophobic⁴⁵ and ionic⁴⁶ SAMs have been used as substrates for cell culture. A significant problem with these preparations is the lack of control over the adsorption process. Studies of the differentiation response of fibroblasts and neuroblastoma cells on siloxane SAMs terminated in different groups coated with fibronectin showed that cell behavior depends upon the conformation of fibronectin and not the density of protein on the surface.^{18, 47}

Patterning the Formation of SAMs.

Microcontact Printing. Microcontact printing (μ CP)⁴⁸⁻⁵⁰ is a convenient method that can pattern SAMs of alkanethiolates on gold in the plane of the monolayer, with features down to 1 μ m conveniently, and to 200 nm in special cases (Figure 4).⁵¹ Microcontact printing uses an elastomeric stamp that is formed by casting polydimethylsiloxane (PDMS) against an appropriate relief structure, usually a photolithographically produced master. The PDMS stamp is inked with a solution of the alkanethiol in ethanol, dried, and manually brought into contact with a gold surface: the alkanethiol is transferred only at those regions where the stamp contacts the surface. Conformal contact between the elastomeric stamp and surface and the rapid reaction of alkanethiols with gold permit the surface to be patterned over areas several cm^2 in size with edge resolution of the features better than 50 nm. Multiple stamps can be cast from a single master and each stamp can be used hundreds of times. Microcontact printing has also been used to pattern siloxanes on the surfaces of SiO_2 and glass⁵¹ and to pattern SAMs on non-planar and contoured surfaces.⁵² Because μ CP is a technique that relies on molecular self-assembly and does not require stringent control over the laboratory environment, it can produce μ m-scale patterns conveniently and at low cost relative to methods that use photolithography.



Figure 4. Procedure for patterning SAMs using microcontact printing. Photolithography or other methods generate a mask containing features of the pattern to be reproduced. A PDMS prepolymer is poured onto the master pattern, allowed to cure (a), and peeled away from the master (b). The stamp is inked with a solution of alkanethiol (c) and used to transfer the alkanethiol to the surface (d); this transfer forms a patterned SAM (the representation of the SAM implies no structure) (e). Exposing the gold substrate to a solution of a different alkanethiol derivatizes the bare regions (f).

Photolithography. Photolithographic methods illuminate a substrate with UV light through a mask containing the pattern to be reproduced.⁵³ In the common "liftoff" method, a silicon oxide substrate is coated with a thin layer of photoresist and irradiated with UV light through a mask. The exposed regions are removed in a developing bath to reveal complementary patterns of silicon dioxide and photoresist. Subsequent immersion of the substrate in a solution of alkyltrichlorosilane forms siloxane SAMs. The remaining photoresist is then removed, and a different siloxane can be formed in the complementary regions. Other variants of photolithography use the UV irradiation to pattern photoreactive SAMs of siloxanes.^{54, 55} The required photolithographic equipment and a controlled environment facility make this technique expensive, and substantially less convenient than μ CP. The ink-jet printing of glucose oxidase on carbon electrodes to fabricate amperometric glucose biosensors⁵⁶ suggests another new and inexpensive method for patterning arrays of biomolecules.

Fabrication of Contoured Surfaces. Both μ CP⁵⁷ and photolithography⁵⁸ have been used to form patterned layers (resists) that protect the substrates from dissolution in chemical etchants. Chemical etching of the patterned SAMs produces contoured features whose shapes depend on the orientation of the silicon and the duration of the etching process; etching lines in a silicon $\langle 100 \rangle$ surface produces V-shaped grooves. The properties of the etched substrates can then be tailored by subsequent formation of an alkylsiloxane SAM or by evaporation of a film of gold followed by formation of an alkanethiolate SAM.

Patterning the Adsorption of Protein. Patterned SAMs on gold have been used extensively to adsorb protein in patterns on surfaces (Fig. 5) This method relies on the property of SAMs terminated in oligo(ethylene glycol) groups to resist adsorption of protein. For example, μ CP was used to generate regions of SAMs terminated in either

Figure 5. Scanning electron microscope (SEM) micrographs of fibrinogen adsorbed on a patterned SAM. A patterned hexadecanethiolate self-assembled monolayer (SAM) on gold was formed by microcontact printing and the remainder of the surface was derivatized by exposure to a hexa(ethylene glycol)-terminated alkanethiol. The patterned substrate was then immersed in a solution of fibrinogen (1 mg/ml in PBS buffer) for two hours, removed from solution, rinsed with water, and dried. Fibrinogen adsorbed only to the methyl-terminated regions of the SAM, and appear as the dark regions in the micrograph. The top image shows a pattern of the type used in the microelectronics industry. The bottom image illustrates the utility of microcontact printing for patterning the adsorption of proteins on the micron scale. Reprinted with permission from: Mrksich M, Whitesides GM. Patterning self-assembled monolayers using microcontact printing: a new technology for biosensors? *Trends in Biotechnology* 1995; 13:228-235. Copyright 1995 Elsevier Science Ltd.

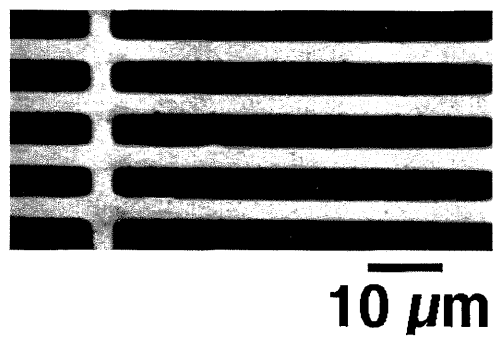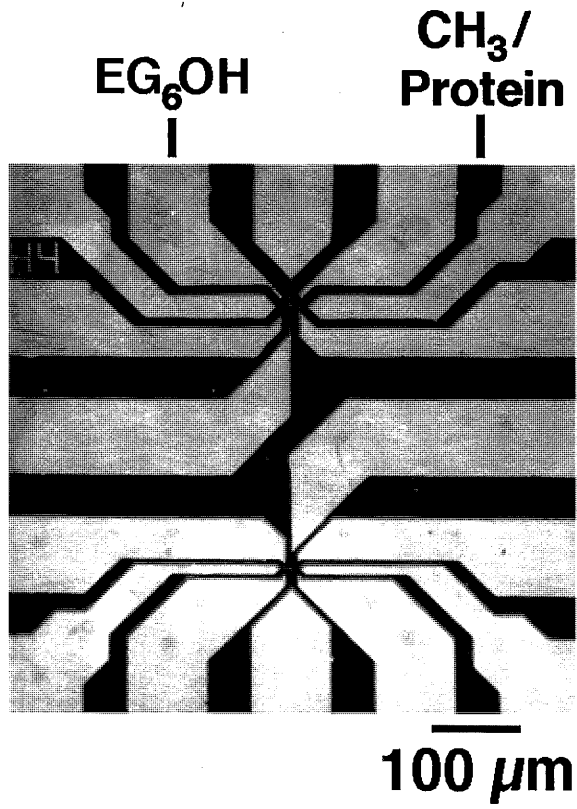

methyl groups (hydrophobic groups) or oligo(ethylene glycol) groups. Immersion of these SAMs in an aqueous solution of protein resulted in the adsorption of a monolayer of protein on the methyl-terminated regions; scanning electron microscopy (SEM) is a particularly convenient technique for imaging the resulting pattern of protein (Fig. 5).⁵⁹ Bhatia et al used photolithography to convert siloxane SAMs terminated with thiol groups to sulfonate groups which resisted the non-specific adsorption of protein; the fluorescent protein phycoerythrin was then covalently linked to the thiol groups in regions that had been protected from UV light by the mask.⁶⁰

Cell Attachment to Patterned SAMs. The same methods used to create patterns of proteins have been used to control the attachment of cells to surfaces:⁶¹⁻⁶⁴ Spargo et al used photolithography to prepare patterned arrays of perfluoro- and amino-terminated siloxane monolayers; endothelial cells preferentially adhered to fibronectin-covered regions of the amino-terminated SAMs and differentiated into neovascular cords.⁶² Amino-terminated siloxanes are excellent substrates for culture of neural cells.⁶³

Microcontact printing was used to pattern SAMs in adhesive lines ranging from 10 μm to 100 μm in width; after coating these substrates with fibronectin, endothelial cells attached and grew only on those lines (Fig. 6). Microcontact printing was similarly used to form SAMs containing adhesive islands (as small as 1600 μm^2) surrounded by oligo(ethylene glycol)-terminated SAMs.⁶⁴ Hepatocytes attached to the laminin-coated hydrophobic islands. DNA synthesis, cell growth, and albumin secretion of the attached hepatocytes was found to be a function of the island size. The use of SAMs to confine growth of cells to specific areas and shapes should increase understanding of the relationship between cell shape and function. The ability to pattern the attachment of individual cells may also be useful for single cell manipulation, toxicology, and drug screening assays.

Figure 6. Controlled attachment of bovine capillary endothelial cells to planar substrates patterned into regions of SAMs terminated in methyl groups and tri(ethylene glycol) groups using microcontact printing. The substrates were coated with fibronectin prior to cell attachment; fibronectin adsorbed only to the methyl-terminated regions of the SAM. (A) The optical micrograph shows attachment of endothelial cells to the non-patterned region at left and to lines 30 μm in width. (B) A view at higher magnification of cells attached to the lines.

Cell Attachment on Contoured Surfaces. Several groups have used surfaces contoured in grooves and ridges--fabricated using photo- or electron beam lithography--to study surface topography on the growth and behavior of attached cells.⁶⁵⁻⁶⁷ Chou and coworkers found that human fibroblasts adherent to surfaces contoured into V-shaped grooves had increased levels of fibronectin synthesis and secretion relative to those grown on smooth surfaces.⁶⁵ Similarly grooved substrata facilitated the *in vitro* healing of flexor tendons relative to planar substrata.⁶⁶ The dimensions of ridges on silicon wafers patterned with arrays of ridges was found to signal differentiation for the fungus *Uromyces*.⁶⁷

Electrochemical Control Over Interfacial Properties. The electrical conductivity of the gold supporting a SAM of alkanethiolates permits a variety of strategies to control the properties of the interface. The wetting properties of SAMs terminated in electroactive groups--for example, ferrocene and quinone groups--were switched reversibly by applying reducing and oxidizing potentials to the gold electrode.⁶⁸ Several groups have immobilized electroactive proteins to SAMs on gold to study electron-transfer reactions of the proteins.⁶⁹ Wong, Langer, and Ingber have shown that the shape and growth of aortic endothelial cells adherent to conducting films of fibronectin-coated polypyrrole were controlled by applying a potential to the substrate.⁷⁰

Prospects. SAMs of alkanethiolates on gold constitute a convenient and broadly useful model system for studying protein adsorption--and processes dependent on protein adsorption--at interfaces. The ability to control precisely the surface chemistry through synthesis, to pattern the formation of SAMs using μ CP, to control the optical and electrical properties of the interface, to employ a variety of analytical techniques that are compatible with SAMs, and to use a variety of substrates--including non-planar and

contoured substrates--permits a wide range of flexibility in tailoring this system for specific applications. A few early demonstrations are described in this chapter; many more will certainly follow.

Acknowledgements

This work was supported by the National Institutes of Health (GM 30367). MVM is grateful to Wellesley College for support of her sabbatical leave and MM is grateful to the American Cancer Society for a postdoctoral fellowship.

References

1. Andrade JD, Hlady V. Protein adsorption and materials biocompatibility: a tutorial review and suggested hypotheses. *Adv Polym Sci* 1986; 79:1-63.
2. Lundstrom I, Ivarsson B, Jonsson U et al. Protein adsorption and interaction at solid surfaces. In: Feast WJ, Munro HS, eds. *Polymer surfaces and interfaces*. John Wiley & Sons Ltd, 1987:201-230.
3. Andrade JD, Hlady V, Wei AP. Adsorption of complex proteins at interfaces. *Pure & Appl Chem* 1992; 64:1777-1781.
4. Wahlfren M, Arnebrant T. Protein adsorption to solid surfaces. *Trends in Biotechnology* 1991; 9:201-208.
5. Sadana A. Protein adsorption and inactivation on surfaces. Influence of heterogeneities. *Chem Rev* 1992; 92:1799-1818.
6. Ramsden JJ. Puzzles and paradoxes in protein adsorption. *Chem Soc Rev* 1995; 73-78.
7. Brash JL. Role of plasma protein adsorption in the response of blood to foreign surfaces. In: Sharma CP and Szycher M, eds. *Blood compatible materials and devices*. Lancaster, Pa: Technomic Publishing Co, Inc., 1991:3-24.
8. Ramsden JJ, Rousch DJ, Gill DS et al. Protein adsorption kinetics drastically altered by repositioning of a single charge. *J Am Chem Soc* 1995; 117:8511-8516.

9. Liedberg B, Lundstrom I, Stenberg E. Principles of biosensing with an extended coupling matrix and surface plasmon resonance. *Sensors and Actuators B* 1993; 11:63-72.
10. Malqvist M. Biospecific interaction analysis using biosensor technology. *Nature* 1993; 361:186-187.
11. Schlatter D, Barner R, Fattinger CH et al. The difference interferometer: application as a direct affinity sensor. *Biosens & Bioelectron* 1993; 8:109-116.
12. Mandenius CF, Welin S, Daneilsson B et al. The interaction of proteins and cells with affinity ligands covalently coupled to silicon surfaces as monitored by ellipsometry. *Anal Biochem* 1984; 137:106-114.
13. Ward MD, Buttry DA. *In situ* interfacial mass detection with piezoelectric transducers. *Science* 1990; 249:1000-1007.
14. Lee D-S, Belfort G. Changing activity of ribonuclease A during adsorption: a molecular explanation. *Proc Natl Acad Sci USA* 1989; 86:8392-8396.
15. Bekos EJ, Ranieri JP, Aebischer P et al. Structural changes of bovine serum albumin upon adsorption to modified fluoropolymer substrates used for neural cell attachment studies. *Langmuir* 1991; 11:984-989.
16. Smith LJ, Clark DS. Measurement of the secondary structure of adsorbed protein by circular dichroism. 1. Measurements of the helix content of adsorbed melittin. *Biochem Biophys Acta* 1992; 1121:111-118.

17. Kondo A, Murakami F, Higashitani K. Circular dichroism studies on conformational changes in protein molecules upon adsorption on ultrafine polystyrene particles. *Biotech Bioengineer* 1992; 40:889-894.
18. Cheng S-S, Chittur KK, Sukenik CN et al. The conformation of fibronectin on self-assembled monolayers with different surface composition: An FTIR/ATR study. *J Colloid Interface Sci.* 1994; 162:135-143.
19. Darst SA, Robertson CR, Berzofsky JA. Adsorption of the protein antigen myoglobin affects the binding of conformation-specific monoclonal antibodies. *Biophys J* 1988; 53:533-539.
20. Vroman L, Adams AL. Adsorption of proteins out of plasma and solution in narrow spaces. *J Coll Inter Sci* 1986; 111:391-402.
21. Zhong M, Lin L, Kallenbach NR. A method for probing the topography and interactions of proteins: Footprinting of myoglobin. *Proc Natl Acad Sci USA* 1995; 92:2111-2115.
22. Caffrey M, Wang J. Membrane-structure studies using x-ray standing waves. *Ann Rev Biophys Biomol Struct* 1995; 24:351-378.
23. Darst SA, Ahlers M, Meller PH et al. Two-dimensional crystals of streptavidin on biotinylated lipid layers and their interactions with biotinylated macromolecules. *Biophys J* 1991; 59:387-396.

24. Dubois LH, Nuzzo RG. Synthesis, structure, and properties of model organic surfaces. *Ann Rev Phys Chem* 1992; 43:437-463.
25. Whitesides GM, Gorman CG. Self-assembled monolayers: Models for organic surface chemistry. In: Hubbard AT, ed. *Handbook of surface imaging and visualization*. Boca Rotan: CRC Press, 1995:713-733.
26. Parikh AN, Allara DL, Azouz IB et al. An intrinsic relationship between molecular structure in self-assembled n-alkylsiloxane monolayers and deposition temperature. *J Phys Chem* 1994; 98:7577-7590.
27. Ulman A. *An introduction to ultrathin organic films: from Langmuir Blodgett to self-assembly*. London: Academic Press, 1991.
28. McGovern ME, Kallery KMR, Thompson M. Role of solvent in the silanization of glass with octadecyltrichlorsilane. *Langmuir* 1994; 10:3607-3614.
29. Allara DL, Parikh A N, Rondelez F. Evidence for a unique chain organization in long chain silane monolayers deposited on two widely different solid substrates. *Langmuir* 1995; 11:2357-2360.
30. Ikada Y. Interfacial biocompatibility. In: Salaby WS, Ikada Y, Langer R, et al, eds. *Polymers of Biological and Biomedical Significance*. ACS Symposium Series 540, Washington, DC, 1994:35-48.
31. Tilton RD, Robertson CR, Gast AP. Manipulation of hydrophobic interactions in protein adsorption. *Langmuir* 1991; 7:2710-2718.

32. Prime KL, Whiteside GM. Self-assembled organic monolayers: model systems for studying adsorption of proteins at surfaces. *Science* 1991; 252:1164-1167.
33. Tengvall P, Lestelius M, Liedber B et al. Plasma protein and antisera interactions with L-cysteine and 3-mercaptopropionic acid monolayers on gold surfaces. *Langmuir* 1992; 8:1236-1238.
34. Gombotz WR, Guanghui W, Horbett TA et al. Protein adsorption to poly(ethylene oxide) surfaces. *J Biomed Mater Res* 1991; 15:1547-1562.
35. Cima LG. Polymer substrates for controlled biological interactions. *J Cell Biochem* 1994; 56:155-161.
36. Amija M, Park K. Surface modification of polymeric biomaterials with poly(ethylene oxide). A steric repulsion approach. In: Salaby WS, Ikada Y, Langer R, et al, eds. *Polymers of Biological and Biomedical Significance*. ACS Symposium Series 540, Washington, DC, 1994:135-146.
37. Prime KL, Whitesides GM. Adsorption of proteins onto surfaces containing end-attached oligo(ethylene oxide); a model system using self-assembled monolayers. *J Am Chem Soc* 1993; 115:10714-10721.
38. Mrksich M, Sigal GB, Whitesides GM. Surface plasmon resonance permits *in situ* measurement of protein adsorption on self-assembled monolayers of alkanethiolates on gold. *Langmuir* 1995; in press.

39. Jeon SI, Lee J H, Andrade JD. Protein-surface interactions in the presence of polyethylene oxide: simplified theory. *J Coll Inter Sci* 1991; 142:149-158.
40. Hong H-G, Jiang M, Sligar S G et al. Cysteine-specific surface tethering of genetically engineered cytochromes for fabrication of metalloprotein nanostructures. *Langmur* 1994; 10:153-158.
41. Kooyman RPH, van den Heuvel DJ, Drijhout JW et al. The use of self-assembled receptor layers in immunosensors. *Thin Films* 1994; 244:913-916.
42. Spinke J, Liley M, Schmitt et al. Molecular recognition at self-assembled monolayers: optimization of surface functionalization. *J Chem Phys* 1993; 99:7012-7019.
43. Sigal GB, Bamdad C, Barberis A et al. A self-assembled monolayer for the binding and study of histidine-tagged proteins by surface plasmon resonance. *Anal Chem* submitted.
44. Mrksich M, Grunwell JR, Whitesides GM. Bio-specific adsorption of carbonic anhydrase to self-assembled monolayers of alkanethiolates that present benzenesulfonamide groups on gold. *J Am Chem Soc* submitted.
45. Lopez GP, Albers MW, Schreiber SL et al. Convenient methods for patterning the adhesion of mammalian cells to surfaces using self-assembled monolayers of alkanethiolates on gold. *J Am Chem Soc* 1993; 115:5877-5878.

46. Margel S, Vogler EA, Firment L et al. Peptide, protein, and cellular interactions with self-assembled monolayer model surfaces. *J Biomed Mater Res* 1993; 27:1463-1476.
47. Lewandowska K, Pergament E, Sukenick CN et al. Cell-type-specific adhesion mechanisms mediated by fibronectin adsorbed to chemically derivatized substrata. *J Biomed Mater Res* 1992; 26:1343-163.
48. Kumar A, Biebuyck HA, Whitesides. Patterning self-assembled monolayers: applications in materials science. *Langmuir* 1994; 10:1498-1511.
49. Mrksich M, Whitesides GM. Patterning self-assembled monolayers using microcontact printing: a new technology for biosensors? *Trends in Biotechnology* 1995; 13:228-235.
50. Wilbur JL, Kumar A, Biebuyck HA et al. Microcontact printing of self-assembled monolayers: applications in microfabrication. *Nanotechnology* 1995; in press.
51. Xia Y, Mrksich M, Kim E et al. Microcontact printing of siloxane monolayers on the surface of silicon dioxide, and its application in microfabrication. *J Am Chem Soc* 1995; 117:9576-9577.
52. Jackman RJ, Wilbur JL, Whitesides GM. Fabrication of submicron features on curved substrates by microcontact printing. *Science* 1995; 269:664-666.
53. Dulcey CS, Georger JH, Krathamer V et al. Deep UV photochemistry of chemisorbed monolayers; patterned coplanar molecular assemblies. *Science* 1991; 252:551-554.

54. Frisbie CD, Wollman EW, Wrighton MS. High lateral resolution imaging by secondary ion mass spectrometry of photopatterned self-assembled monolayers containing aryl azide. *Langmuir* 1995; 11:2563-2571.
55. Pritchard DJ, Morgan H, Cooper J M. Patterning and regeneration of surfaces with antibodies. *Anal Chem* 1995; 67:3605-3607.
56. Newman JD, Turner APF, Mararazza G. Ink-jet printing for the fabrication of amperometric glucose biosensors. *Anal Chim Acta* 1992; 262:13-17.
57. Kim E, Kumar A, Whitesides GM. Combining patterned self-assembled monolayers of alkanethiolates on gold with anisotropic etching of silicon to generate controlled surface morphologies. *J Electrochem Soc* 1995; 142:628-633.
58. Britland S, Clark P, Connolly P et al. Micropatterned substratum adhesiveness: A model for morphogenetic cues controlling cell behavior. *Exp Cell Res* 1992; 198:124-129.
59. Lopez GP, Biebuyck HA, Harter R et al. Fabrication and imaging of two-dimensional patterns of proteins adsorbed on self-assembled monolayers by scanning electron microscopy. *J Am Chem Soc* 1993; 115:10774-10781.
60. Bhatia SK, Hickman JJ, Ligler FS. New approaches to producing patterned biomolecular assemblies. *J Am Chem Soc* 1992; 114:4432-4433.

61. Kleinfeld D, Kahler KH, Hockberger PE. Controlled outgrowth of dissociated neurons on patterned substrates. *J Neuroscience* 1988; 8:4098-4120.
62. Spargo BJ, Testoff MA, Neilsen TB et al. Spatially controlled adhesion, spreading, and differentiation of endothelial cells on self-assembled molecular monolayers. *Proc Natl Acad Sci USA* 1994; 91:11070-11074.
63. Stenger DA, Georger JA, Dulcey CS et al. Coplanar molecular assemblies of amino- and perfluorinated alkylsilanes: Characterization and geometric definition of mammalian cell adhesion and growth. *J Am Chem Soc* 1992; 114:8435-8442.
64. Singhvi R, Kumar A, Lopez GP et al. Engineering cell shape and function. *Science* 1994; 264:696-698.
65. Chou L, Firth JD, Uitto V-J et al. Substratum surface topography alters cell shape and regulates fibronectin mRNA level, mRNA stability, secretion and assembly in human fibroblasts. *J Cell Sci* 1995; 108:1563-1573.
66. Wójciak B, Crossan J, Curtis ASG et al. Grooved substrata facilitate *in vitro* healing of completely divided flexor tendons. *J Materials Sci: Materials in Medicine* 1995; 6:266-171.
67. Hock HC, Staples RC, Whitehead B et al. Signaling for growth orientation and cell differentiation by surface topography in *Uromyces*. *Science* 1987; 235:1659-1662.

68. Abbott N, Whitesides GM. Potential-dependent wetting of aqueous solutions on self-assembled monolayers formed from 15-(ferrocenylcarbonyl)pentadecanethiol on gold. *Langmuir* 1994; 10:1493-1497.
69. Tarlov MJ, Bowden EF. Electron-transfer reactions of cytochrome c adsorbed on carboxylic acid terminated alkanethiol monolayer electrodes. *J Am Chem Soc* 1991; 113:1847-1849.
70. Wong JY, Langer R, Ingber, DE. Electrically conducting polymers can noninvasively control the shape and growth of mammalian cells. *Proc Natl Acad Sci USA* 1994; 91:3201-3204.